


# Installation Guide K-60 HS70

High shrink two piece protective bulk roll with separate closure

## Product Description

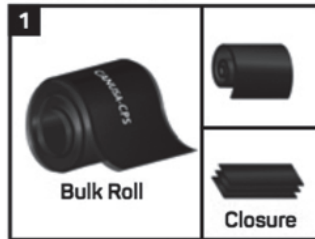


K-60 HS70 (CanusaWrap™) is typically shipped in bulk rolls. Closures are shipped either in bulk rolls or pre-cut. The adhesive is protected from contamination by an inner liner. High Shrink sleeves are used with tyton, flange, coupling, and casing joint applications.

## Equipment List



Propane tank & torch; Appropriate tools for surface abrasion; Knife, roller, rags & solvent cleanser; Temperature measuring device; Standard safety equipment; gloves, goggles, hard hat, etc.

## Product Preparation - Sleeve

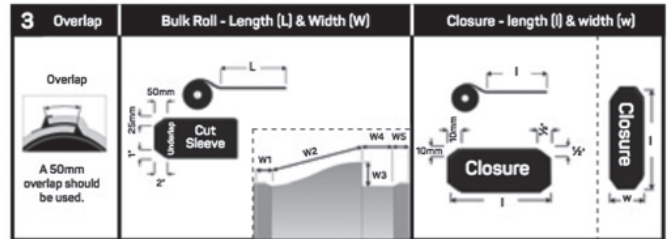

3 **Overlap**  
A 50mm overlap should be used.

**Bulk Roll - Length (L) & Width (W)**  
Cut the required length (L) of sleeve material from the bulk roll. The length should be calculated using the circumference of the joint+150mm  
 $L = \text{Joint O.D.} + 150\text{mm}$


**Closure - length (l) & width (w)**  
Cut the required length (l) of closure material from the bulk roll.  
 $l = \text{sleeve width} \text{ less } 5\text{mm}$

Ensure that there is no damage, dirt or moisture on the sleeve.

4 **Width (W)**  
Cut the required width (W) of WLOX material from the bulk roll. The width should be calculated using the contours of the joint.  
 $W = W1 + W2 + W3 + W4 + W5$


Ensure that there is no damage, dirt or moisture on the sleeve.

## Surface Preparation

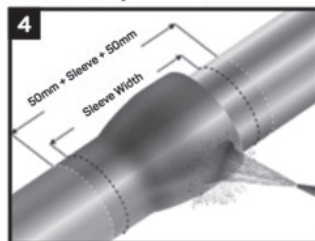

Ensure that the pipe is dry before cleaning. Prepare the steel joint area to a minimum of St2 /SP2. Lightly abrade the pipe coating adjacent to the weld area to a distance of 50mm (2") beyond each end of the sleeve width.


## Flame Intensity & Torch Size

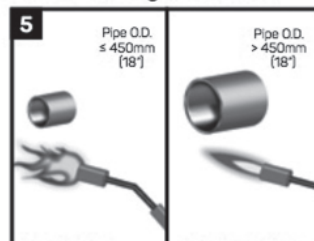

5 **Pipe O.D. ≤ 450mm (18")**  
Use moderate flame intensity for pre-heating and shrinking.  
Minimum Torch Size: 150,000 BTU/hr.

**Pipe O.D. > 450mm (18")**  
Use moderate to high flame intensity for pre-heating and shrinking.  
Minimum Torch Size: 300,000 BTU/hr.

## Pre-Heat

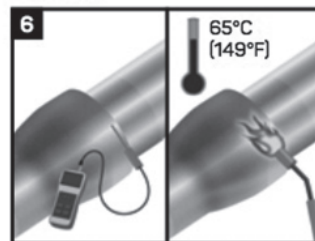


6 Pre-heat the joint area to a minimum of 65°C (149°F). Using a temperature measuring device, ensure that the correct temperature is reached on the steel and at least 50mm (2") on each side of the sleeve.


## Sleeve Installation




7 Partially remove the release liner and gently heat the underlap approximately 150mm (6") from the edge.

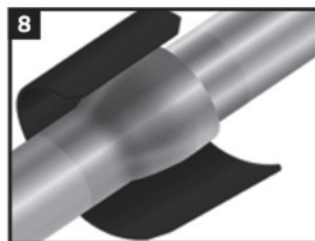


8 Centre the sleeve over the joint so that the sleeve overlaps between the 10 and 2 o'clock positions. Press the underlap firmly into place and remove the remaining release liner.

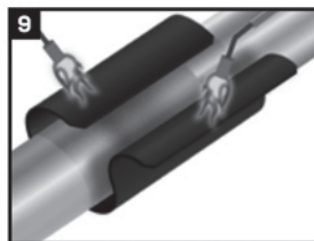

9 Wrap the WLOX sleeve around the tyton joint. Gently heat the backing of the underlap and the adhesive side of the overlap. Finish wrapping the sleeve around the tyton joint pressing the overlap firmly into place.

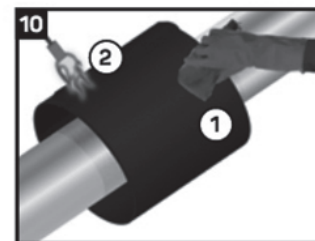


10 1. Clean the overlap area of the sleeve where the closure is to be applied.  
2. Pre-warm the overlap area where the closure is to be placed.

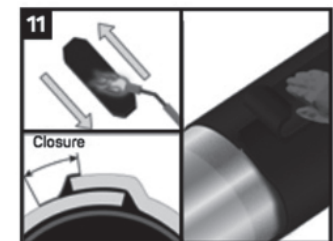


11 Warm the adhesive side of the closure until it becomes shiny. Centre the closure over the overlap. Using a gloved hand press the closure firmly down onto the overlapping sleeve.

## Installation Guide K-60 HS70


High shrink two piece protective bulk roll with separate closure

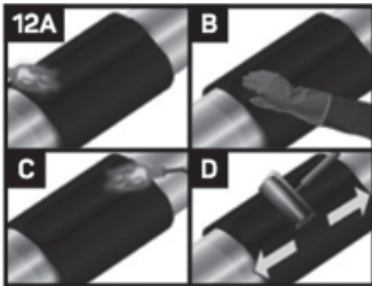


Gently heat the closure and pat it down with a gloved hand. Repeating this procedure, move from one side to the other. Smooth any wrinkles by gently working them outward from the centre of the closure with a roller.

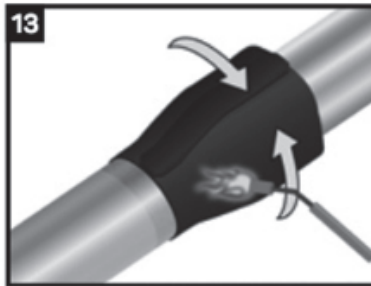


Using broad strokes, begin shrinking the sleeve around the entire circumference of the larger end (bell) of the tyton joint. Continue heating from the centre of the sleeve until sleeve recovery is completed around the bell of the tyton joint.

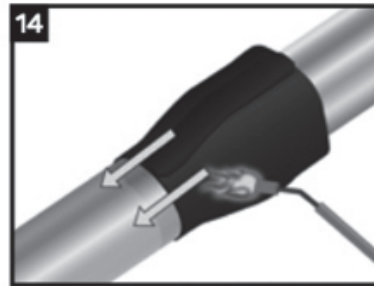


Continue shrinking from the bell of the tyton joint to the sleeve end. Sleeve recovery is complete when it conforms to the pipe.

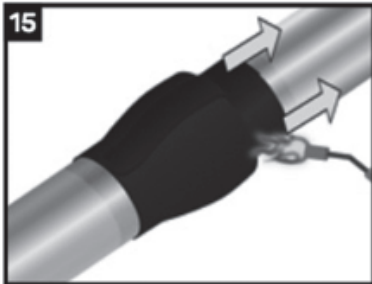

If the closure lifts while shrinking, secure it with a gloved hand. Continue heating from the bell of the tyton joint to the other end (spigot) until recovery is complete.

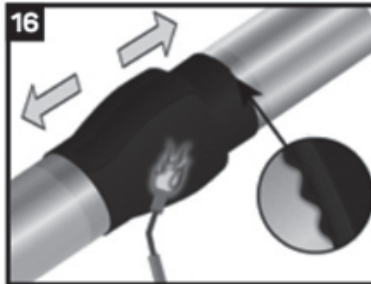


In a similar manner, heat and shrink the remaining side. Shrinking has been completed when the adhesive begins to ooze at the sleeve edges all around the circumference.

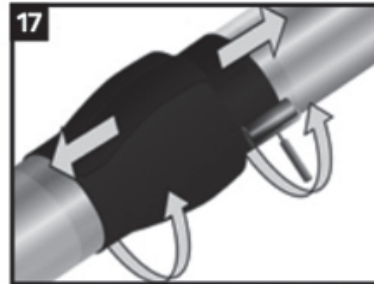

While the sleeve is still hot and soft, use a hand roller to firmly roll the sleeve surface and push any trapped air up and out of the sleeve, as shown above. If necessary, reheat to roll out air.

### Quality Check (Finger Probe Test)

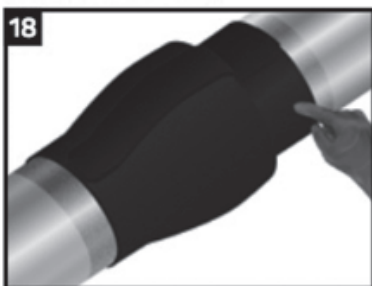

With a gloved hand, press down on the installed sleeve to ensure the backing and sleeve are soft. If there are any cool spots, the sleeve should be reworked with additional heat.

### Inspection



Visually inspect the installed sleeve for the following:

- Sleeve is in full contact with the tyton joint
- No lifts between sleeve and closure
- Adhesive flows beyond both sleeve edges
- No cracks or holes in sleeve backing

 **CANUSA-CPS**  
Corrosion Protection & Sealing

### Backfilling Guidelines

After shrinking is complete, allow the sleeve to cool to below the intended operating temperature of the pipeline before backfilling. To prevent damage to the sleeve, use selected backfill material, (no sharp stones or large particles) otherwise an extruded polyethylen mesh or other suitable shield should be used.